



Fatigue damage evolution in fibre composites for wind turbine blades

Jespersen, Kristine Munk; Lowe, Tristan; Withers, Philip J.; Mikkelsen, Lars Pilgaard

Publication date:
2015

[Link back to DTU Orbit](#)

Citation (APA):

Jespersen, K. M., Lowe, T., Withers, P. J., & Mikkelsen, L. P. (2015). *Fatigue damage evolution in fibre composites for wind turbine blades*. Poster session presented at Ph.D. Course 2015: Fracture Mechanics for Laminated Composite Structures, Aalborg, Denmark.

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.


Fatigue damage evolution in fibre composites for wind turbine blades

Kristine M. Jespersen^{1*}, Tristan Lowe², Philip J. Withers², and Lars P. Mikkelsen¹

¹Department of Wind Energy, Technical University of Denmark, (*kmun@dtu.dk)

²Manchester X-Ray Imaging Facility, School of Materials, University of Manchester


Unidirectional (UD) glass fibre composites are used for wind turbine blades due to their high stiffness to weight ratio. One of the main limiting factors of increasing the blade length is the lack of knowledge on fatigue damage evolution, making it necessary to include high safety factors. This study focuses on fatigue behaviour through 3D X-ray Computed Tomography (CT) experiments and Finite Element Method (FEM) simulations.

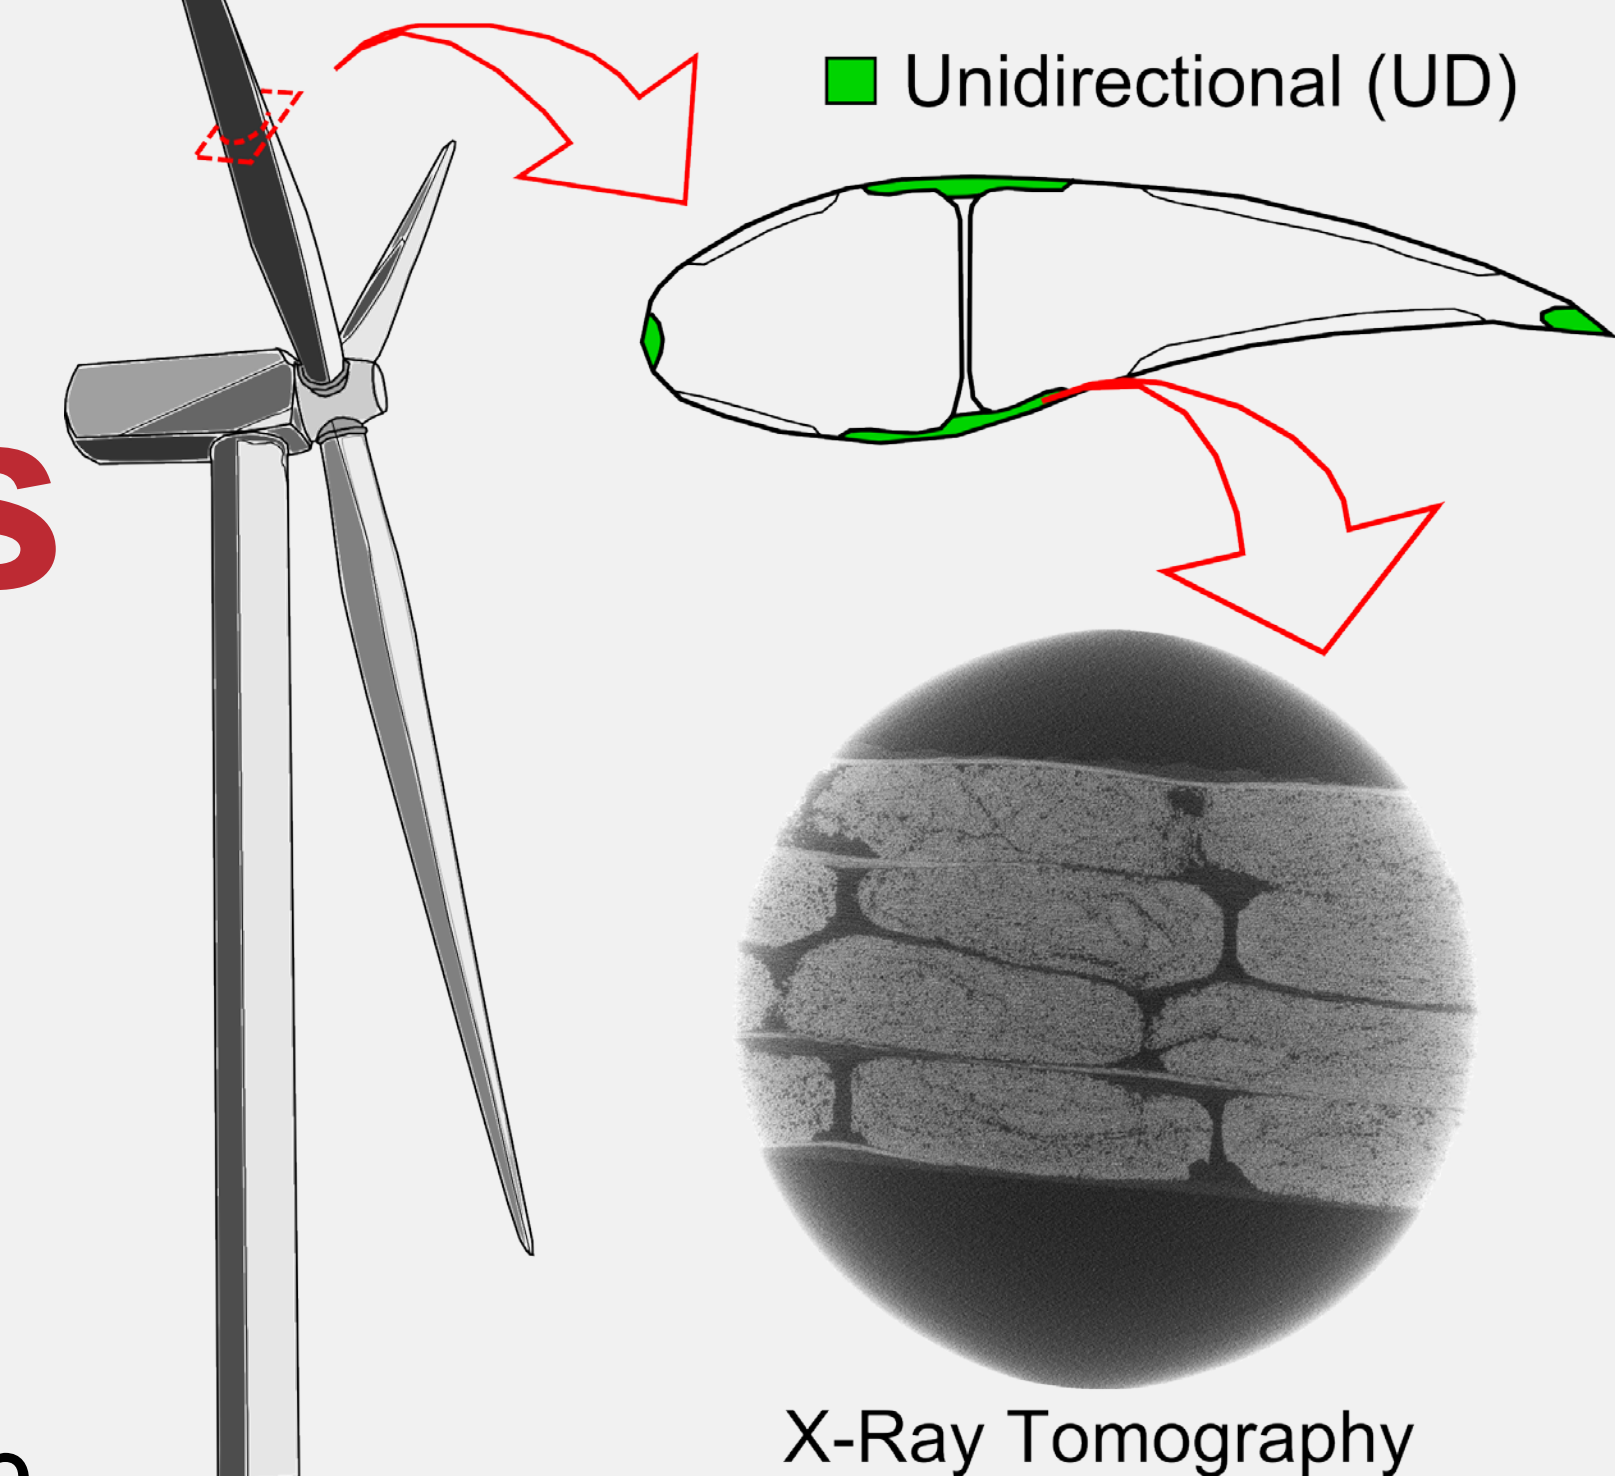

X-Ray Tomography
UD glass fibre composite material is used for the load carrying parts of the wind turbine blade considered (marked with green). The glass fibres are gathered in bundles which are held in place by stitching them to a backing layer. The glass fibres are in the range of 17-21 microns in diameter and are surrounded by a polyester resin.

Overall Approach

In this PhD project, 3D X-ray Computed Tomography (CT) is used to observe fatigue damage over time and to characterize the microstructure. The experimental results from the non-destructive X-ray CT experiments are used as a basis for FEM modelling using the commercial software ABAQUS.

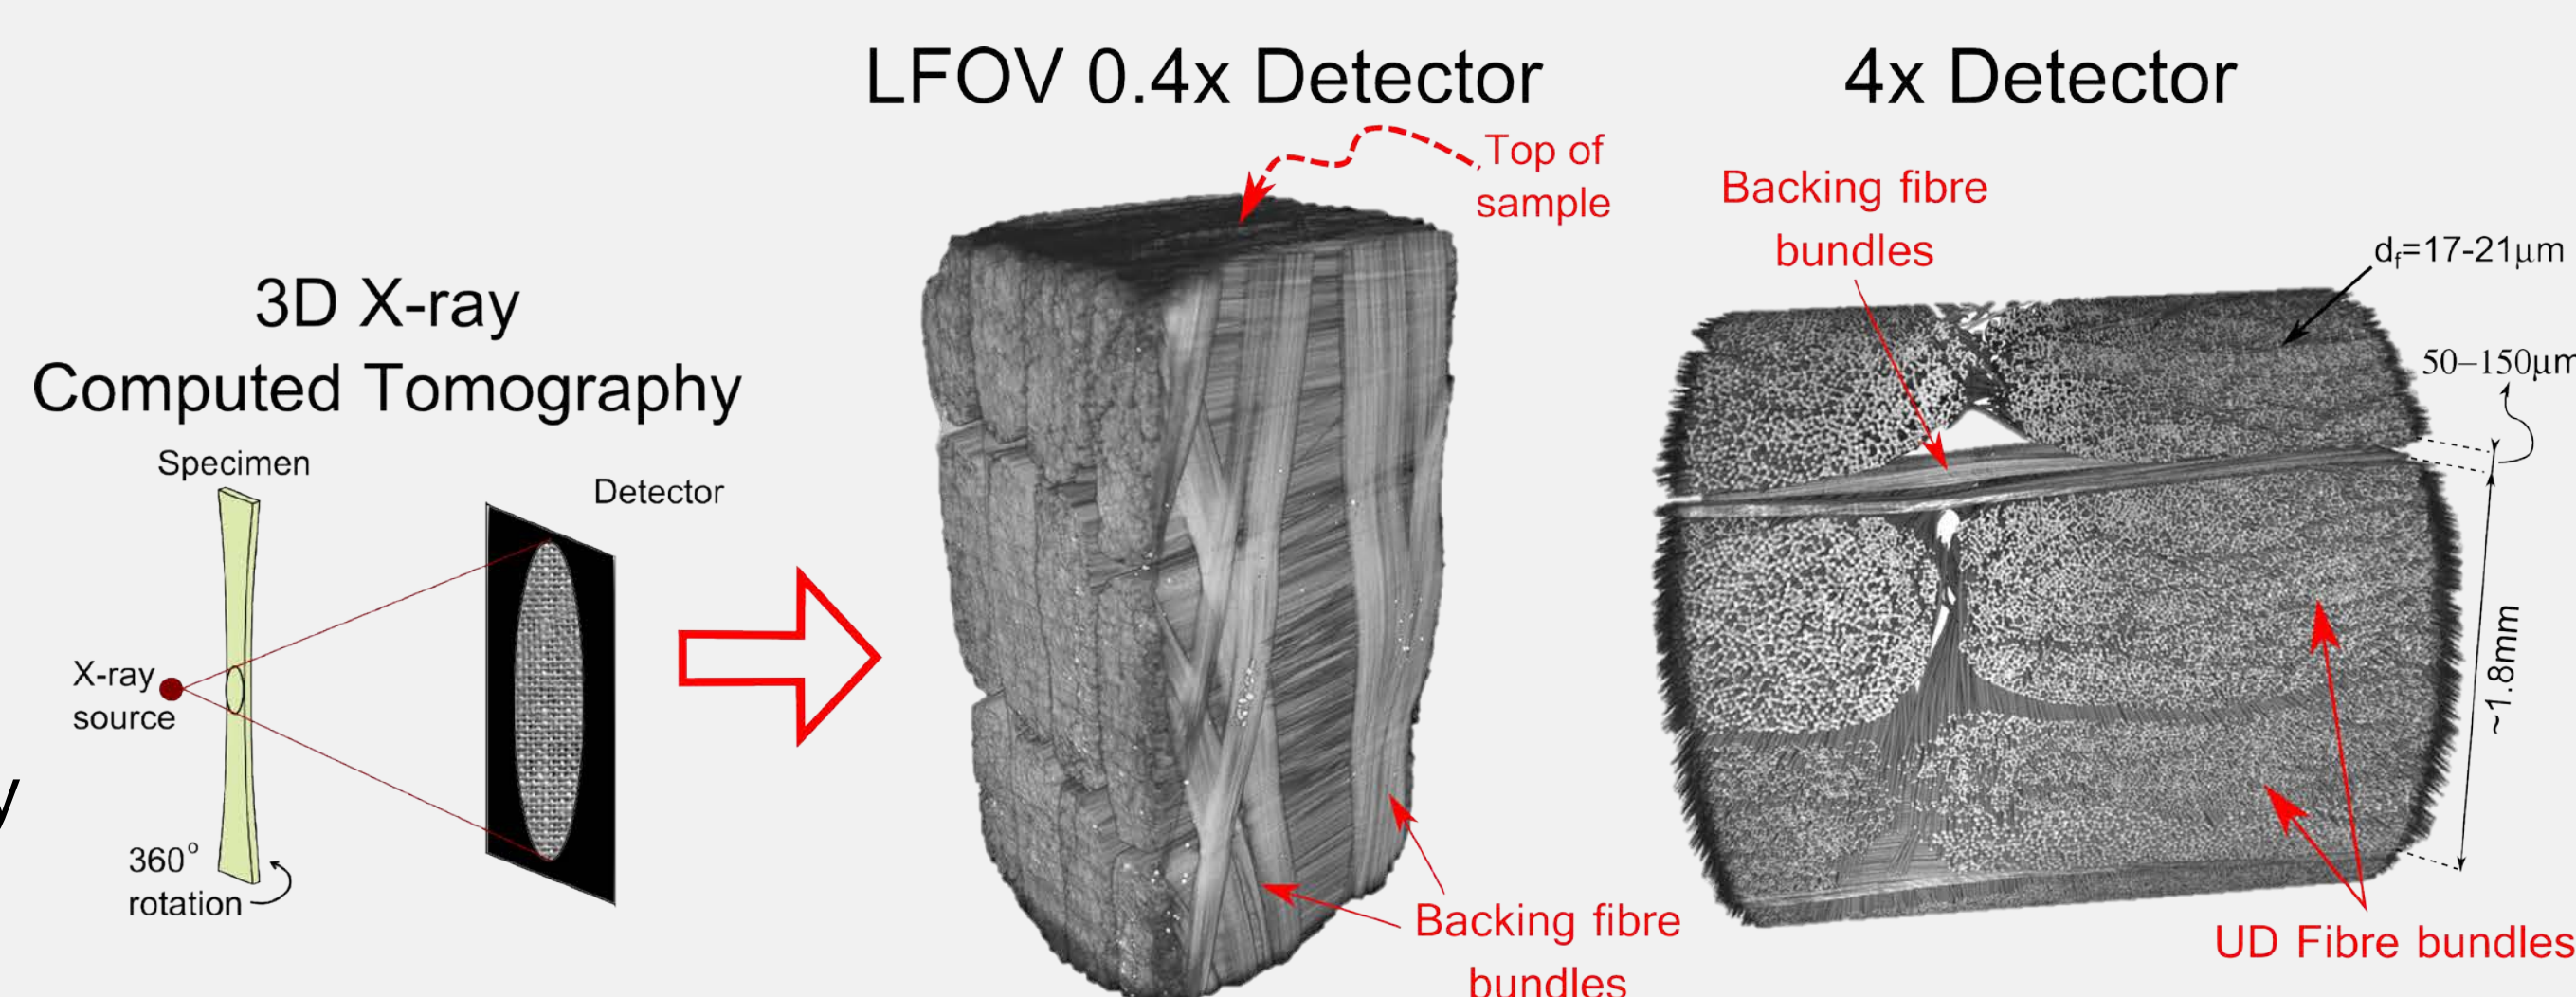


3D X-ray CT

3D X-ray CT is a non-destructive imaging technique where the sample is placed between an x-ray source and a detector and x-rays are emitted through the sample which creates a projection image on the detector. The sample is rotated in steps for each of which a projection image is stored. An algorithm is then used to reconstruct a 3D image from the 2D projection images.

Fatigue Damage Observation

The fatigue damage in the material will be found over time by performing ex-situ start-stop fatigue tests where the sample is scanned using 3D X-ray CT at different time steps during the tension-tension fatigue test.

The damage in the material can be visualized and segmented for each time step.

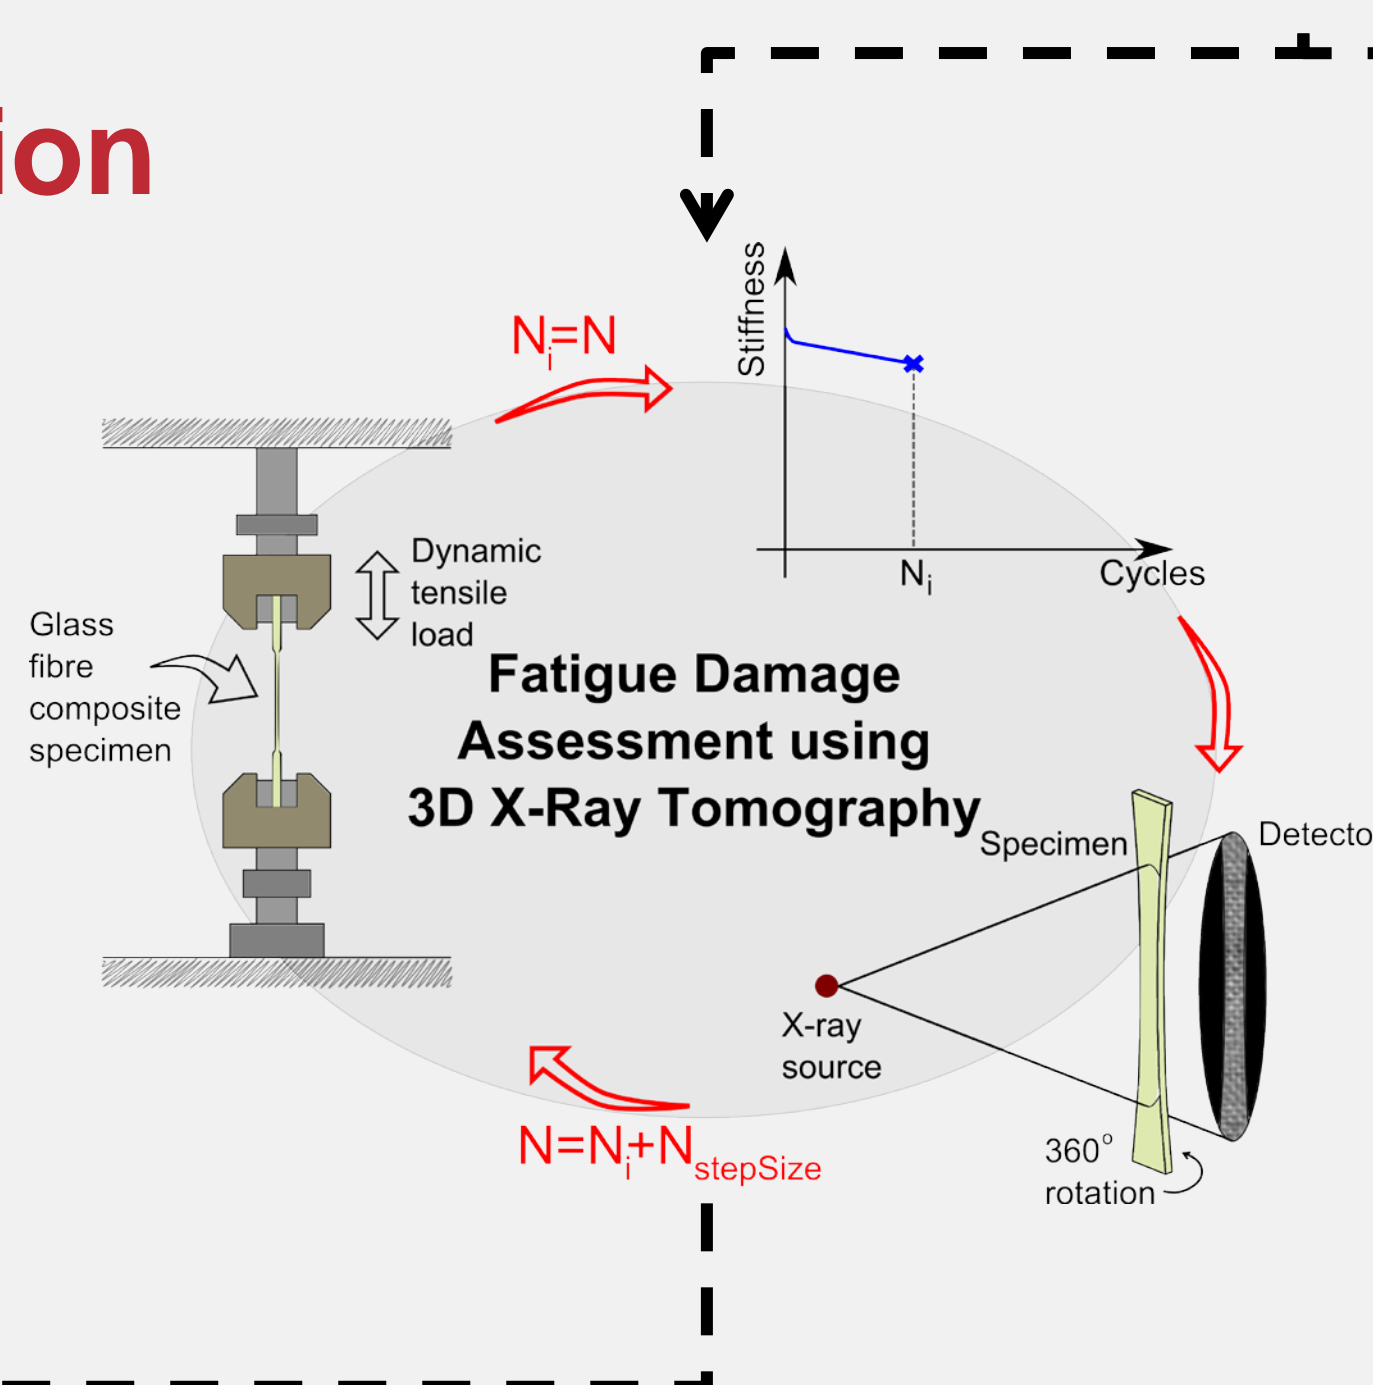


Quantification of Microstructure


From the 3D image obtained of the microstructure, image processing algorithms are applied to extract microstructural parameters:

- Fibre centre lines by slice by slice coordinates
 - Fibre diameters related to each individual fibre
- From these parameters, additional parameters will be calculated:
- Fibre misalignment
 - Fibre contact point
 - Local fibre volume fraction

Fibre centre lines and diameters algorithm

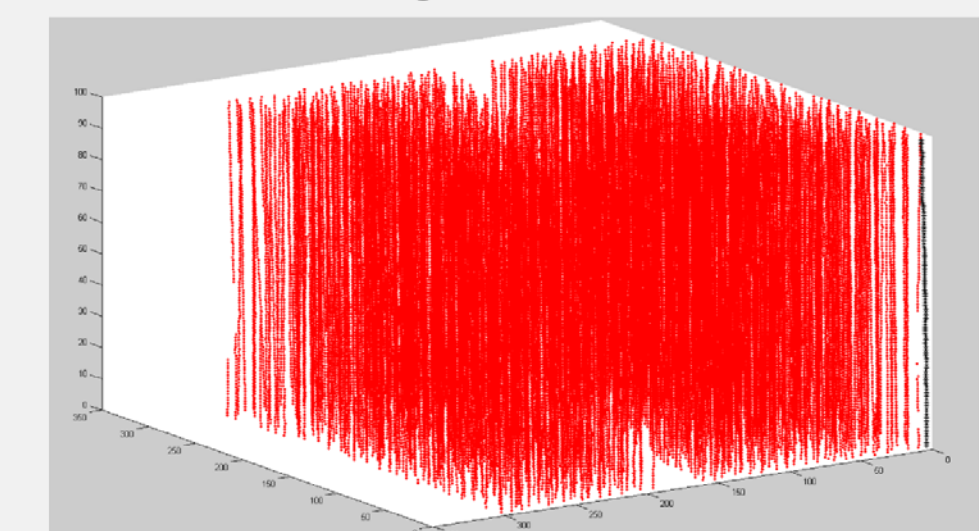

Visualization and Segmentation of broken fibres

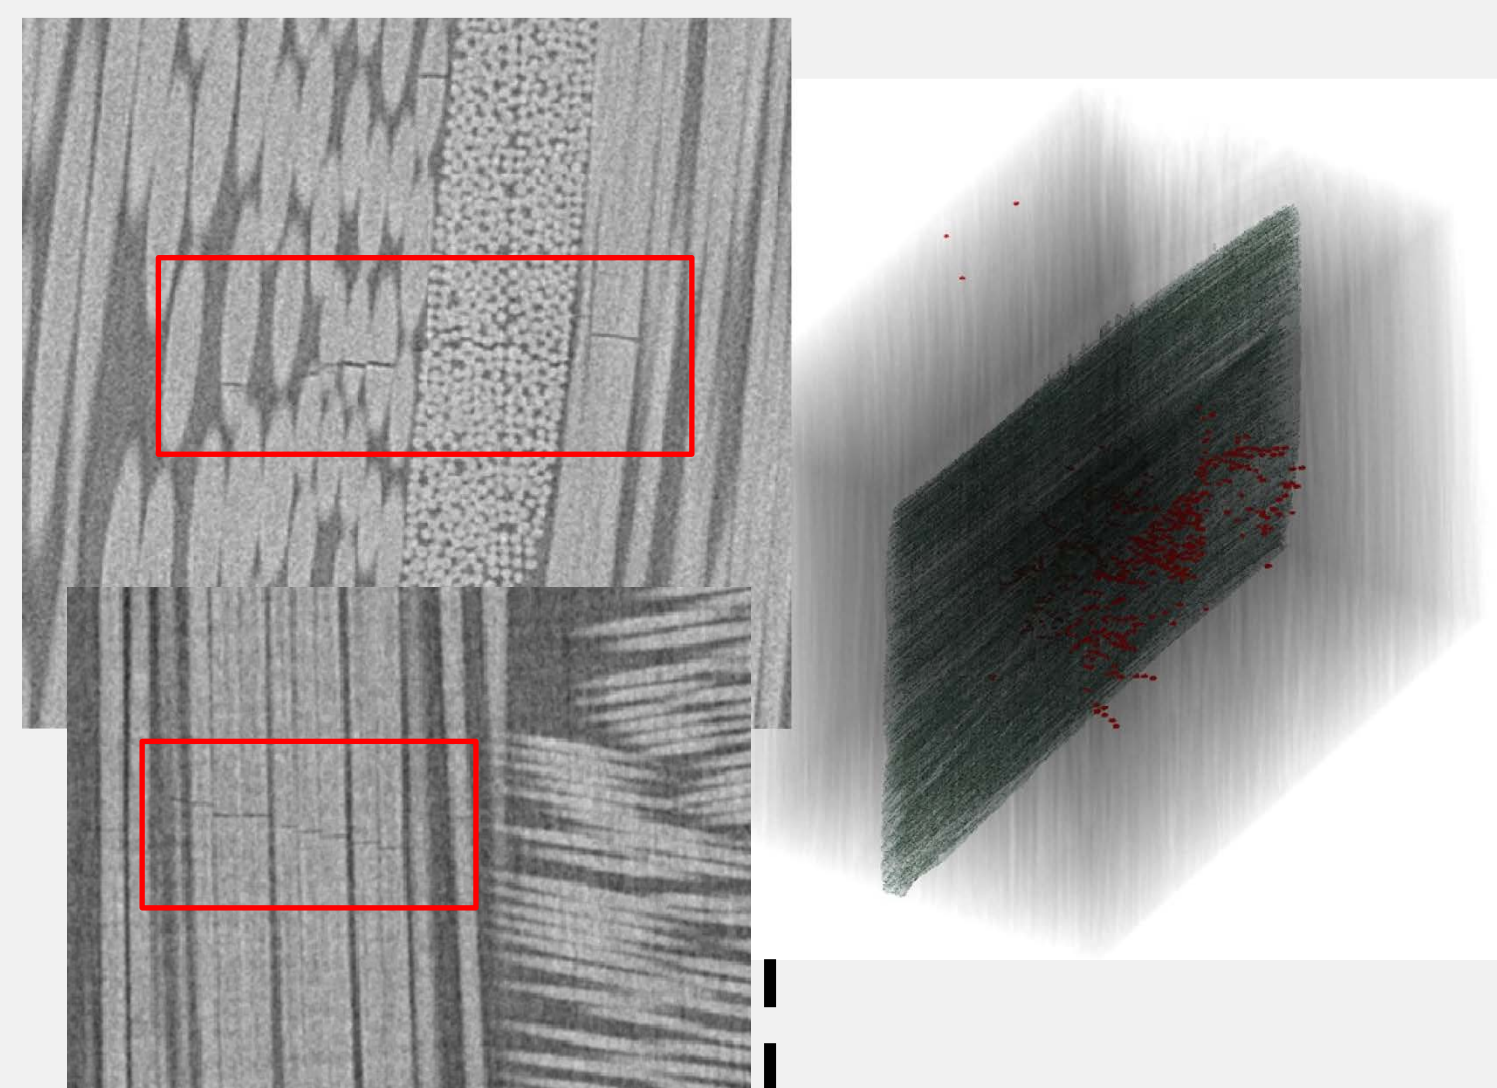


ABAQUS Modelling

The modelling part of this project is still in its initial part, and at this point the fibres can be imported into ABAQUS and meshed.

The following is planned to be carried out in the future:

- Introduce fibre fracture into the imported volume and view effect on stiffness etc.
- Include supporting off-axis backing bundles and their local effect on fibre fracture of the load carrying UD fibres
- Use quantified microstructural parameters to generate an equivalent volume on which fatigue properties can be evaluated.

Python script for import into ABAQUS for further analysis

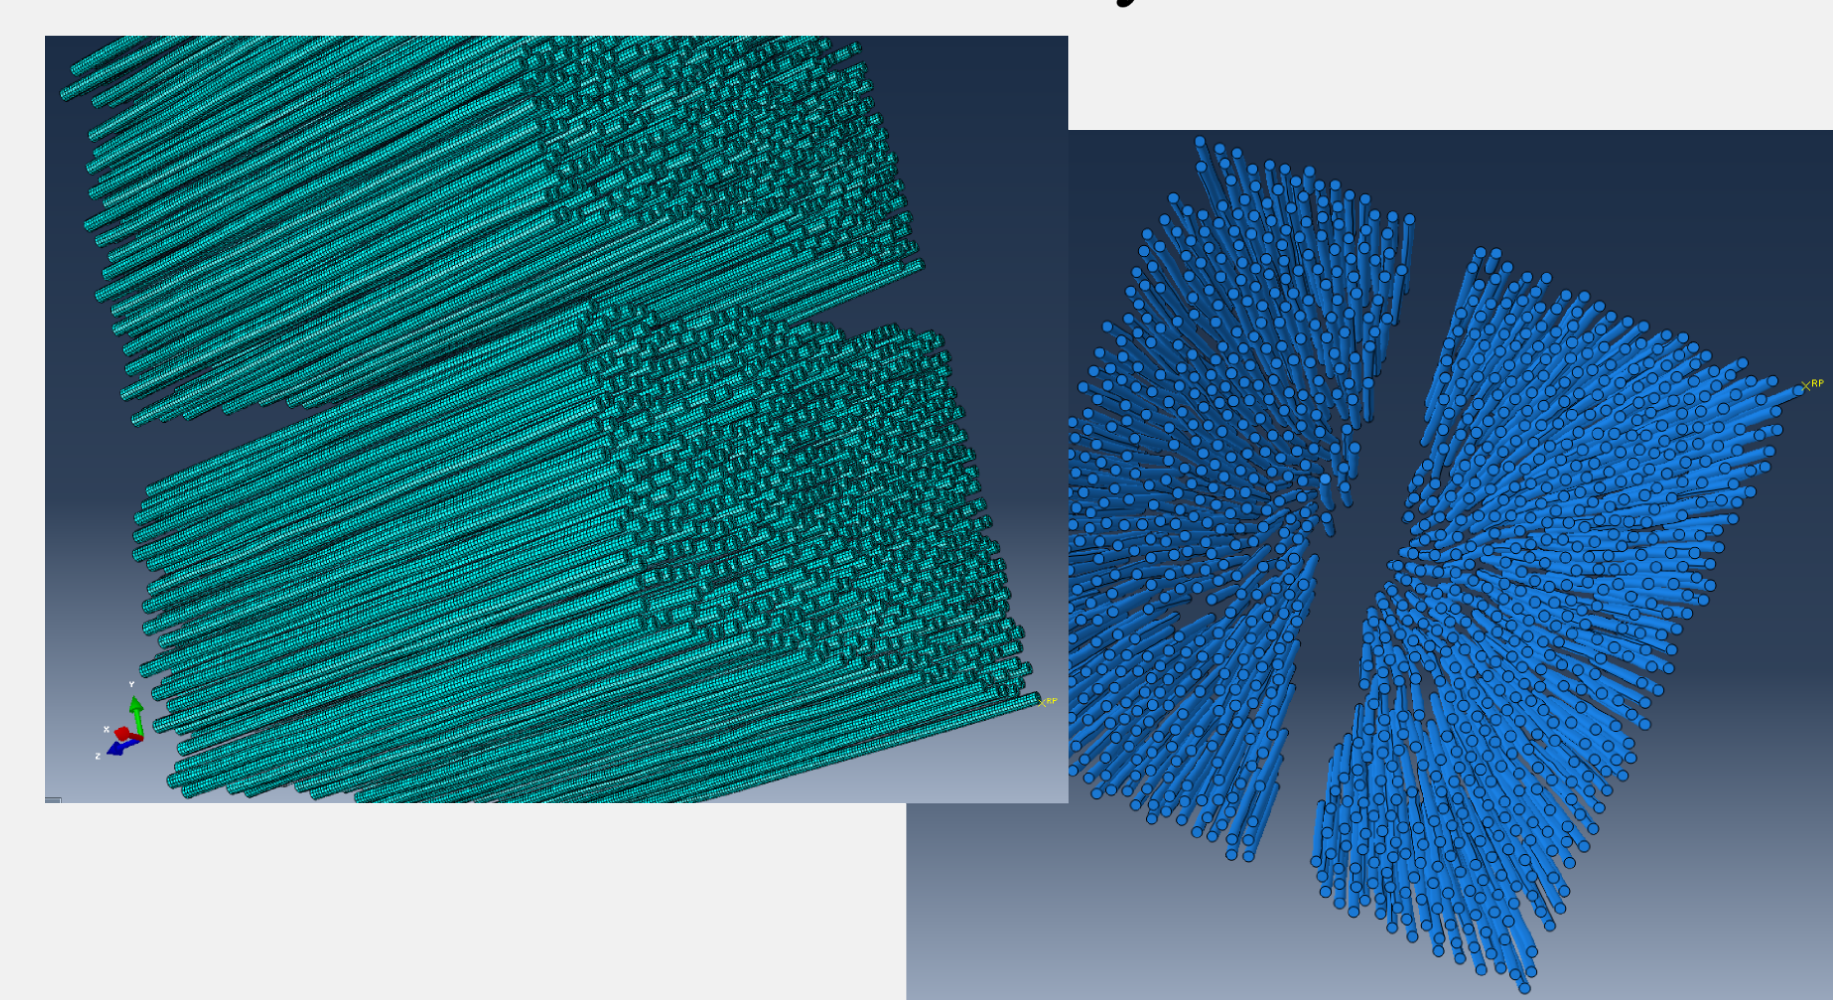

Utilize knowledge to create a realistic FEM model and for validation

Acknowledgements

- We would like to acknowledge the assistance provided by the Manchester X-ray Imaging Facility, which was funded in part by the EPSRC (grants EP/F007906/1, EP/F001452/1 and EP/I02249X/1)
- Financial support from CINEMA: "the allianCe for ImagiNg of Energy MAterials", DSF-grant no. 1305-00032B under "The Danish Council for Strategic Research" is gratefully acknowledged.
- We would like to thank LM Wind Power for manufacturing of test specimens.

References

- R.P.L. Nijssen, 2006. *Fatigue life prediction and strength degradation of wind turbine rotor blade composites*, PhD thesis, Delft University of Technology.
- J.Z Hansen, 2013. *The effects of fibre architecture on the fatigue life-time of composite materials*, PhD thesis, Technical University of Denmark.
- M.J. Emerson, K.M. Jespersen, P.S. Jørgensen, R. Larsen, A.B. Dahl, *Dictionary Based Segmentation in Volumes*, Springer International Publishing Switzerland, SCIA 2015, LNCS 9127, pp.505-516